arXiv:cond-mat/9610140v1 [cond-mat.supr-con] 17 Oct 1996

$SO(5)$ Quantum Nonlinear σ Model Theory of the High T_c Superconductivity

Shou-Cheng Zhang

Department of Physics, Stanford University, Stanford, CA 94305

(February 1, 2008)

Abstract

We show that the complex phase diagram of high T_c superconductors can be deduced from a simple symmetry principle, a $SO(5)$ symmetry which unifies antiferromagnetism with d wave superconductivity. We derive the approximate $SO(5)$ symmetry from the microscopic Hamiltonian and show furthermore that this symmetry becomes exact under the renormalization group flow towards a bicritical point. With the help of this symmetry, we construct a $SO(5)$ quantum nonlinear σ model to describe the effective low energy degrees of freedom of the high T_c superconductors, and use it to deduce the phase diagram and the nature of the low lying collective excitations of the system. We argue that this model naturally explains the basic phenomenology of the high T_c superconductors from the insulating to the underdoped and the optimally doped region.

In search of a low energy effective theory The high T_c superconductors are among the most complex systems ever studied in condensed matter physics. In order to reach to the core of the physics responsible for this novel phenomenon, we obviously have to cross many different energy scales, and integrate away irrelevant degrees of freedom. Earlier in the high T_c development, Anderson [1], Zhang and Rice [2] argued rather successfully that a good starting point for modeling the strong correlation effects in the oxides should be the Hubbard, or the $t-J$ model close to half filling. Unfortunately, both of the these models are still too difficult treat. Their exact solutions in one dimension shed very little light on how to solve these models in higher dimensions.

Even within the much simplified Hubbard or $t-J$ model close to half filling, there are two different energy scales in the problem. There is a piece of "high energy physics", which is responsible for forming local singlet pairs. This piece of physics is not very subtle, and basically originates from the J term in the Hamiltonian. We can associate a temperature, T_{MF} with this energy scale, which can be between zero and $1000K$, depending on the filling factor. For conventional BCS superconductors, the energy scale of the pair formation is the same as the true phase transition temperature into a superconducting state. However, for the oxides, this piece of "high energy physics" does not tell us about the true ground state of the system.

Back in 1987, Lee and Read [3] asked a thought provoking question, "Why is the T_c so low?". If the singlet formation is the same as superconducting transition, the natural transition temperature would be the same as T_{MF}, much higher than the observed T_c. The reason that the T_c is low is because there is another "low energy physics", valid below T_{MF}, which governs the fate of the singlet pair. The singlet pairs can form a spatially order state, leading to a antiferromagnetic ground state, they can condense, to form a d wave superconductor, they can arrange themselves into a spatially non-uniform state and lead to phase seperation [4], they can form a spatially homogenous mixed state of coexisting antiferromagnetic and superconducting order, a "spin bag phase" [5], and finally, the effects of quantum fluctuation can be strong enough to destroy any form of order parameter, leading

to a "resonating valence bond (RVB) phase" [1]. In order to sort out the different competing ground states, we need a effective Hamiltonian which describes this "low energy physics" sector of the $t-J$ model, valid below T_{MF}. It should be a simple Hamiltonian which can be solved analytically, and yet, the complexity of the possible phases should emerge from the unity of the model and the simplicity of its mathematical solution.

What is the principle which can guide us in the search of such a universal low energy Hamiltonian? The different competing orders are not separated by any obvious energy scales in the remaining problem. Therefore, it is not obvious how one can systematically apply the renormalization group idea to integrate out the irrelevant degrees of freedom. Fortunately, whenever Nature poses us a extraordinary difficult challenge involving strongly interacting low energy degrees of freedom, it often times gives away its secret in the *symmetry* of the problem. Symmetry principle, exact or approximate, served us very well in our quest of the laws of nature, and it appears to be the only principle which can help us to solve the highly complex high T_c problem. The main idea is to identify the symmetries of the microscopic Hamiltonian, such as the $t-J$ model, and use the symmetry to constrain the possible form of the low energy effective Hamiltonian.

What symmetries should we use, and what symmetries remain to be discovered? Well, we know the low energy effective Hamiltonian of a antiferromagnet, it is the $SO(3)$ quantum nonlinear σ model. Chakravaty, Halperin and Nelson [6] showed convincingly that the physical properties of the undoped oxides are well described by this model. More recently, Pines and coworkers [7,8], Chubukov, Sachdev and Ye [9] argued that this model is applicable in the underdoped regime as well. We also know the low energy effective Hamiltonian of a superconductor, it is described by a $U(1)$ quantum nonlinear σ model, or sometimes called the XY model. Doniach and Inui [10] attempted to describe the metal insulator transition in terms of a quantum XY model, and recently, Emery and Kivelson [11] presented evidence that the superconducting transition on the underdoped side of the oxides can be described by a renormalized classical XY model. Both the $SO(3)$ spin rotation and the $U(1)$ charge rotation symmetries are the obvious symmetries of the microscopic $t-J$ model, and should

certainly be used as constraining symmetries of the new, unified low energy theory.

The simplest way to construct a unified theory of antiferromagnetism and superconductivity is to introduce a concept which I call a *superspin*[1]. It is a five dimensional vector, $n_a = (n_1, n_2, n_3, n_4, n_5)$. The first and the fifth components are the *super*conducting components of the *superspin*, identified with the two d wave superconducting order parameters [12,8]

$$\begin{aligned} & n_1 = \Delta^\dagger + \Delta \quad , \quad n_5 = -i(\Delta^\dagger - \Delta) \\ & \Delta^\dagger = \sum_p g(p) c^\dagger_{p\uparrow} c^\dagger_{-p\downarrow} \quad , \quad g(p) = cosp_x - cosp_y \end{aligned} \tag{1}$$

The remaining three components are the *spin* components of the *superspin*, identified with the antiferromagnetic order parameter

$$n_2 = \sum_p c^\dagger_{p+Q,i} \sigma^x_{ij} c_{p,j} \quad , \quad n_3 = \sum_p c^\dagger_{p+Q,i} \sigma^y_{ij} c_{p,j} \quad , \quad n_4 = \sum_p c^\dagger_{p+Q,i} \sigma^z_{ij} c_{p,j} \tag{2}$$

where σ^α's are the Pauli spin matrices and $\vec{Q} = (\pi, \pi, \pi)$ is the antiferromagnetic ordering vector. The concept of the superspin is similar to that of the pseudospin [13,14], with a crucial difference that pseudospin is really "pseudo" in the sense that it has no real spin component. There is a $SO(3)$ spin symmetry acting on the (n_2, n_3, n_4) subspace, with the total spin S_α being the generator of the rotation, and there is a $U(1)$ charge symmetry acting on the (n_1, n_5) subspace, with the total charge Q being the rotation generator,

$$S_\alpha = \sum_p c^\dagger_{p,i} \sigma^\alpha_{ij} c_{p,j} \quad , \quad Q = \frac{1}{2}(N - M) \tag{3}$$

Here N is the number of electrons and M is the number of lattice sites. Of course, the concept of the *superspin* would only be useful if we can enlarge the known $SO(3) \times U(1)$ symmetry group, to include orthogonal transformations which can rotate the antiferromagnetic order parameters into the superconducting ones. The minimal group to accomplish this would be

---

[1]I would like to thank Prof. R.B. Laughlin for a stimulating discussion which helped me to form this concept.

a $SO(5)$ symmetry group. If such orthogonal transformations exists, and if they commute with the microscopic Hamiltonian, then the concept of the *superspin* would be a very useful one. Since the orthogonal transformations preserve the magnitude of the vector, we can impose the constraint

$$n_a^2 = 1 \tag{4}$$

and really think of the *superspin* as a vector of a fixed magnitude in a five dimensional space, where the antiferromagnetic and superconducting order appear as three and two dimensional projections of this five dimensional vector.

But we need 10 different "Euler angles" to describe a general rotation in a 5 dimensional space, mathematically speaking, the $SO(5)$ group has 10 symmetry generators. (In general, the $SO(n)$ group has $n(n-1)/2$ symmetry generators). The known $SO(3) \times U(1)$ symmetry supplies us with 4 such generators, where are the remaining 6 generators?

Enter the π operators and the $SO(5)$ algebra Fortunately, the remaining 6 symmetry generator have already been discovered by Demler and Zhang [15], in their recent work on the theory of the resonant neutron scattering of the high T_c superconductors. These operators carry charge 2, spin 1, and a total momentum (π, π, π). Here we will call them π operators, and they are defined as follows

$$\pi_\alpha^\dagger = \sum_p g(p) c_{p+Q,i}^\dagger (\sigma^\alpha \sigma^y)_{ij} c_{-p,j}^\dagger \quad , \quad \pi_\alpha = (\pi_\alpha^\dagger)^\dagger \tag{5}$$

and we see that there are obviously six of them.

Let us recall that the $SO(5)$ Lie algebra has ten generators $L_{ab} = -L_{ba}$ satisfying the following commutation relations

$$[L_{ab}, L_{cd}] = i(\delta_{ac} L_{bd} - \delta_{ad} L_{bc} - \delta_{bc} L_{ad} + \delta_{bd} L_{ac}) \tag{6}$$

Let us identify the ten operators $(Q, S_\alpha, \pi_\alpha, \pi_\alpha^\dagger)$ with the generators of the $SO(5)$, L_{ab}, in the following way,

$$L_{ab} = \begin{pmatrix} 0 & & & & \\ \pi_x^\dagger + \pi_x & 0 & & & \\ \pi_y^\dagger + \pi_y & -S_z & 0 & & \\ \pi_z^\dagger + \pi_z & S_y & -S_x & 0 & \\ Q & -i(\pi_x^\dagger - \pi_x) & -i(\pi_y^\dagger - \pi_y) & -i(\pi_z^\dagger - \pi_z) & 0 \end{pmatrix} \tag{7}$$

where the value of the matrix elements on the upper right triangle are determined by anti-symmetry, $L_{ab} = -L_{ba}$. Using the fermionic representations of the $(Q, S_\alpha, \pi_\alpha, \pi_\alpha^\dagger)$ in equations (3), (5), and the above identification, we can check explicitly that the $SO(5)$ commutation relations (6) are indeed satisfied provided that we make the continuum approximation

$$g^2(p) \approx 1 \tag{8}$$

This approximation is valid when we consider the long wave length limit, where the only important information about the internal structure of a composite operator is its symmetry, but its detailed shape. Since $g^2(p)$ has a s wave symmetry, we approximate it by its average value.

With the aid of the $SO(5)$ algebra, the concept of the superspin introduced earlier can be defined precisely. *The superspin n_a is defined as a vector representation of the $SO(5)$ Lie algebra*, satisfying the following commutation relation

$$[L_{ab}, n_c] = -i\delta_{bc} n_a + i\delta_{ac} n_b \tag{9}$$

If we substitute for L_{ab} and n_c the microscopic definitions in terms of the electron operators (1), (2) and (7), we find that they are indeed satisfied in the continuum approximation (8). In particular, we see that the π operators rotate the antiferromagnetic order parameter into superconducting order parameter and vice versa. Therefore, the six π operators [15] recently introduced by Demler and Zhang are exactly the six missing symmetry generators we are searching for.

With the basic low energy variables assembled and their kinematic relations fully specified, we are now in a position to address the dynamic properties, and discuss the commuta-

tion relations between the symmetry generators L_{ab} and the microscopic $t-J$ Hamiltonian. The total spin operators L_{23}, L_{24}, L_{34} and the total charge operator L_{15} certainly commute exactly with the $t-J$ Hamiltonian. What about the remaining six generator?

Demler and Zhang [15] have shown that although they do not commute exactly with the Hamiltonian, they are approximate eigenoperators of the $t-J$ Hamiltonian, in the sense that

$$[\mathcal{H}, \pi_\alpha^\dagger] = \omega_0 \ \pi_\alpha^\dagger \tag{10}$$

where $\omega_0 = J(1-n)/2 - 2\mu$. The way to obtain this relation is by the standard t matrix approximation, similar to the random-phase-approximation for particle-hole operators. The reason that this relation hold is rather simple. The $\pi_\alpha^\dagger$ operator is a particle particle operator, describing a pair of electrons with a center of mass momentum $\vec{Q} = (\pi, \pi, \pi)$. However, for tight binding models with nearest neighbor hopping, the two particle continuum vanishes at $\vec{Q}$. Therefore, a repulsive interaction, such as J in the triplet channel, naturally leads to a antibound state. ω_0 in the above equation is nothing but the energy eigenvalue of this antibound state. More sophisticated calculations beyond the t matrix approximation have also been carried out recently [16,17]. Equation (10) is a fundamental equation underlying the present work, it provides a bridge from the microscopic $t-J$ Hamiltonian to the effective nonlinear σ model theory. One can also define a π' operator, using $g(p) = cosp_x + cosp_y$ in equation (5). Such a operator would transform antiferromagnetism to s wave superconductivity. However, it was found [15] that they are in general not eigenoperators. Therfore, our theory naturally predicts d pairing symmetry.

There are two reasons why the $SO(5)$ symmetry is only a approximate one. One is the approximation used to derived equation (10). Therefore, this relation should be tested in exact diagonalization studies of the Hubbard or the $t-J$ model. This can be done by calculating the dynamical correlation functions of the π operators and identifying isolated poles in their spectral function. Fortunately, such a study has been carried out recently by Meixner and Hanke [18], there is indeed a sharp collective mode in the π channel. The second

reason why the $SO(5)$ symmetry is broken explicitly is that even if (10) holds exactly, the Hamiltonian does not commute with all generators of $SO(5)$. However, this source of explicit symmetry breaking is easy to handle, and has interesting physical consequences which we will explore throughout this paper. The eigenoperator relation (10) is almost as good as the vanishing of the commutator. The reason is that the Casimir operator $C = \sum_{a<b} L_{ab}^2$ of the $SO(5)$ algebra commutes with the Hamiltonian, and therefore, we can still classify all the eigenstates of the Hamiltonian according to their $SO(5)$ quantum numbers. This also means that the superspin vector multiplet n_a is not mixed into other higher tensorial representations of the $SO(5)$ under time evolution, a crucial fact which enables us to construct a low energy effective Hamiltonian containing the superspin degrees of freedom only. The situation is very analogous to the problem of a spin precessing in a magnetic field. While the full spin rotation symmetry is broken by the magnetic field, the magnitude of the spin is preserved.

So far I have tried to present the line of arguments according to the logical reasoning in the high T_c problem. However, at this stage, it would be appropriate to reveal the historic origin and the source of inspiration which lead to the present work. The present work is a generalization of the concept of the exact $SO(4)$ symmetry [19] of the Hubbard model and its application to the negative U Hubbard model [14,20,21]. Using the η operators constructed earlier by Yang [22], Yang and Zhang [19] pointed out that the Hubbard model has in additional to the usual $SO(3)$ spin rotation symmetry also a $SO(3)$ pseudospin symmetry generated by the following operator,

$$\eta^\dagger = \sum_p c_{p+Q\uparrow}^\dagger c_{-p\downarrow}^\dagger \quad , \quad \eta = (\eta^\dagger)^\dagger \quad , \quad \eta_0 = Q \tag{11}$$

While this symmetry is valid both for the positive and the negative U Hubbard model, the simplest vector multiplet contains s wave superconducting and charge density wave order parameter [14,20],

$$\Delta_s^\dagger = \sum_p c_{p\uparrow}^\dagger c_{-p\downarrow}^\dagger \quad , \quad \Delta_0 = \sum_{p\alpha} c_{p+Q,\alpha}^\dagger c_{p,\alpha} \quad , \quad \Delta_s = (\Delta_s^\dagger)^\dagger \tag{12}$$

and is therefore only useful for the negative U model. The simplest generalization of the

pseudospin symmetry to the positive U or the $t-J$ model is the concept of the superspin introduced in this work, the precise correspondence between these two symmetries are summarized in table I.

Construction of the $SO(5)$ quantum nonlinear σ model With the basic kinematic and dynamic constraints assembled, we are in a good position to construct a low energy effective Hamiltonian. But before we do so, a critical reader may be concerned with the fact that the $SO(5)$ symmetry is only approximately valid. How do we address this question? Well, it may be useful to look at a historical example where a approximate symmetry was used solve a important physics problem. The quantum chromodynamics (QCD) is a model of strong interaction. Unlike the quantum electrodynamics, it can not be solved perturbatively. However, in the limit of vanishing quark masses, the QCD Lagrangian has a $SU(2)\times SU(2)$ symmetry, with conserved vector and axial currents. In real world, the quarks have small (compared to the natural QCD energy scale) but finite masses, so that the axial current is only approximately conserved. The idea behind the hypothesis of partially conserved axial current (PCAC) is to construct a effective nonlinear σ model assuming that the axial currents were conserved, and then add small explicit symmetry breaking terms to reflect the effects of finite quark masses. The nonperturbative, low energy dynamics of the QCD is essentially understood in this way. Therefore, we will follow the same strategy here to extract the low energy content of the $t-J$ model. Along the way, we shall encounter a pleasant surprise, although the $SO(5)$ symmetry that we start from is approximate, near a critical point, it becomes exact under the renormalization group flow.

Let us first assume that the $SO(5)$ symmetry were a exact symmetry, and ask what is the form of the low energy Hamiltonian. As we argued before, below T_{MF}, the system has a tendency to form local singlets, but it has not fully decided whether to become antiferromagnetic or superconducting in its ground state. Therefore, we can think of T_{MF} as a mean field transition below which the superspin acquires a fixed magnitude, leaving its orientation as a low energy degrees of freedom. Close to T_{MF}, the anisotropy terms in the superspin space are not very important, and this transition can be simply described by a standard

Landau free energy functional

$$F = a|\vec{n}|^2 + b|\vec{n}|^4 \tag{13}$$

T_{MF} is the temperature below which the coefficient of the quadratic term $a = a'(T - T_{MF})$ changes sign.

Below T_{MF}, the magnitude of the superspin is fixed, we can always rescale it to satisfy the constraint (4). The ten generators of $SO(5)$ describe the orthogonal rotation of the superspin, leaving its magnitude fixed. Having either antiferromagnetism or superconductivity corresponds to a fixed direction of the superspin, thus breaking the $SO(5)$ symmetry spontaneously. The low energy dynamics of such a system is determined completely in terms of the Goldstone bosons and their nonlinear interactions as specified by the $SO(5)$ symmetry. The kinetic energy of the system is simply that of a $SO(5)$ rigid rotor, given by $\frac{1}{2\chi}\sum_{a<b} L_{ab}^2(x)$. The quantity χ is nothing but the moment of inertia of the rigid rotor. If we assume the exact $SO(5)$ invariance, and rescale the magnitude of the superspin to satisfy the constraint (4), there are no polynomial terms in the potential energy, and in the long wave length limit, we can perform a gradient expansion to obtain a term $\frac{\rho}{2}\sum_a(\partial_k n_a(x))^2$ to the leading order. Therefore, the resulting Hamiltonian density is given by

$$H_s = \frac{1}{2\chi}\sum_{a<b} L_{ab}^2(x) + \frac{\rho}{2}\sum_a(\partial_k n_a(x))^2 \tag{14}$$

H_s is a unique low energy Hamiltonian constrained by the $SO(5)$ symmetry. However, this symmetry is not exact, therefore, we should allow some weak symmetry breaking perturbations. Of course one should break the $SO(5)$ symmetry in such a way that the subgroup $SO(3) \times U(1)$ of the spin and charge symmetry is still exact. Physically, this corresponds to going from a symmetric rotor of only one moment of inertia to a asymmetric rotor with different moments of inertia. The asymmetric Hamiltonian is given by

$$H_a = \sum_{a<b}\frac{1}{2\chi_{ab}}L_{ab}(x)^2 + \sum_{a<b}\frac{\rho_{ab}}{2}(v_{ab}^k(x))^2 + V(n) \tag{15}$$

where $\chi_{15} = \chi_c$, $\chi_{23} = \chi_{24} = \chi_{34} = \chi_s$ and $\chi_{1(2,3,4)} = \chi_{(2,3,4)5} = \chi_\pi$ are the charge, spin and the newly introduced "π" susceptibility, and we have also introduced a generalized velocity

field $v^k_{ab} = n_a \partial_k n_b - n_b \partial_k n_a$ and the corresponding stiffness in the charge ($\rho_{15} = \rho_c$), spin ($\rho_{23} = \rho_{24} = \rho_{34} = \rho_s$) and the π ($\rho_{1(2,3,4)} = \rho_{(2,3,4)5} = \rho_\pi$) channel. In the presence of explicit symmetry breaking, we also allow a quadratic symmetry breaking term of the form

$$V(n) = -\frac{g}{2}(n_2^2 + n_3^2 + n_4^2) \tag{16}$$

H_s and H_a describe the system at half filling only. In order to go away from half filling, one simply has to add a chemical potential term $-2\mu Q = -2\mu L_{15}$, to obtain $\mathcal{H}_s = H_s - 2\mu L_{15}$ and $\mathcal{H}_a = H_a - 2\mu L_{15}$ respectively. This Hamiltonian is to be quantized using the commutation relations (6) and (9), and a complete set of equations of motion can be determined.

Given the Hamiltonian $\mathcal{H}_a$, one can simply perform a Legendre transformation and obtain the corresponding Lagrangian. After a simple Wick rotation $t \to i\tau$, the Lagrangian density becomes

$$\mathcal{L}_a = \sum_{a<b} \frac{\chi_{ab}}{2} \omega_{ab}(x)^2 + \sum_{a<b} \frac{\rho_{ab}}{2} (v^k_{ab}(x))^2 + V(n) \tag{17}$$

where

$$\omega_{ab} = n_a(\partial_\tau n_b - iB_{bc} n_c) - (a \to b) \tag{18}$$

is the angular velocity. Here we have introduced a set of generalized external potentials B_{ab} coupling to L_{ab}. In our current problem, the only nonvanishing component is $B_{15} = -B_{51} = 2\mu$. The partition function of the system is given by

$$\mathcal{Z} = \int [dn_a] \delta(n^2 - 1) e^{-\int_0^\beta d\tau \int d^d x \mathcal{L}_a} \tag{19}$$

It is now appropriate to define the constants appearing in the model. χ_s and χ_c are the familiar uniform spin susceptibility and charge compressibility of the system, while ρ_s and ρ_c are the spin stiffness and charge stiffness respectively (ρ_s should not be confused with the superfluid density which sometimes also uses this notation). χ_π and ρ_π are the two constants newly introduced in this work. They describe the time and length scale over which

a antiferromagnetic region can be converted to a superconducting region and vice versa. In order for the $SO(5)$ symmetry to be approximately valid, one would require these constants are close in value. The last remaining constant of our model is the anisotropy constant g, which selects either a "easy plane" in the superconducting space (n_1, n_5), or a "easy sphere" in the antiferromagnetic space (n_2, n_3, n_4), depending on the sign of g. As argued before, $\mu = 0$ defines the model at half filling, where we know the system is antiferromagnetic. Therefore, we fix $g > 0$ to match this fact. At this moment, the values of the constants (especially the sign of g) of the model are not deduced from any first principle calculations. However, once these values are fixed at half filling, we will not allow them to vary in a arbitrary fashion. As we shall see in the next few sections, the richness of phase diagram comes entirely from the variation of the chemical potential.

Origin of superconductivity At half filling, we choose $g > 0$ so that the superspin prefers to lie in a "easy sphere" of (n_2, n_3, n_4). Away from half filling, the only new term appearing in the Hamiltonian is just the chemical potential term in $\mathcal{H}_a$. When we investigate the Lagrangian $\mathcal{L}_a$, we observe that the chemical potential term appear as a "gauge coupling" in the imaginary time direction. A constant chemical potential term is a "pure gauge" and could therefore be "gauged away". One's naive expectation would be that such a term has no dynamic consequences. However, one has to pay a price for doing so. Although a constant chemical potential term can be gauged away in the bulk, it reappears as a twisted boundary condition in the imaginary time direction, and could have non-trivial consequences.

It is more direct to investigate the Lagrangian (17) with the periodic boundary condition in the imaginary time direction. Because of the periodic boundary condition, the classical path extremizing the path integral are the static solutions. For the static solutions, we see that the only nonvanishing contribution of the kinetic energy is the chemical potential term, which gives a effective potential energy

$$V_{eff} = V(n) - \frac{(2\mu)^2}{2}(n_1^2 + n_5^2)[\chi_c(n_1^2 + n_5^2) + \chi_\pi(n_2^2 + n_3^2 + n_4^2)] \tag{20}$$

Let us first take the $SO(5)$ symmetric situation where $\chi_\pi = \chi_c = \chi$, in this case the terms

in the square bracket reduces to χ. If we were dealing with a abelian XY model, such a term still does not have any dynamical consequences. Since $n_1^2 + n_5^2 = 1$ in such a case, the above term reduces to a number and gives only a trivial shift of the ground state energy, and can not lead to any nontrivial phase transitions. However, if the XY symmetry is embedded into a higher symmetry group, as is done in the present case, this term has a profound dynamic consequence. While the g term with $g > 0$ favors a antiferromagnetic "easy sphere" (n_2, n_3, n_4), the chemical potential term favors a superconducting "easy plane" (n_1, n_5). This competition leads to a first order (for more detailed discussion of the order of the transition, see a later section) phase transition when

$$\mu = \mu_c = \frac{1}{2}\sqrt{g/\chi} \tag{21}$$

For $\mu < \mu_c$, the ground state is antiferromagnetic, and the superconducting state has a finite energy. This energy decreases gradually as one increases μ, until a level crossing at μ_c. For $\mu > \mu_c$, the situation is reversed, the ground state is superconducting, and the antiferromagnetic state has a finite energy.

For $\chi_\pi \neq \chi_c$, the situation is a bit more complex. In the parameter regime $\chi_c > \chi_\pi$, there is always a first order direct transition from antiferromagnetism to superconductivity at $\mu = \mu_c = \frac{1}{2}\sqrt{g/\chi_c}$. On the other hand, in the parameter regime $\chi_c < \chi_\pi < 2\chi_c$, and for

$$\frac{g}{\chi_\pi} < (2\mu)^2 < \frac{g}{2}\frac{1}{\chi_c - \chi_\pi/2} \tag{22}$$

there exists a intermediate "spin bag" phase [5] with coexisting antiferromagnetic and superconducting order. Schrieffer, Wen and Zhang [5] describe such a phase in terms of pairing the eigenstates of the antiferromagnetic background. It is amusing to observe that when expressed back in terms of the orginal electron operators, their order parameter is a mixture of the antiferromagnetic, d wave superconducting order parameter *and* the π operators.

The above discussion based on the Lagrangian may appear rather formal for some readers, a intuitive physical example would be useful. Consider a antiferromagnet with a easy axis anisotropy (say the z axis). Below the Neel transition, the Neel vector prefers to point

along the easy axis. A uniform magnetic field pointed along the easy axis creates a easy xy plane. At a critical value of the magnetic field, there is a "spin flop" transition where the Neel vector changes its orientation from the z axis to the xy plane. Once the underlying $SO(5)$ symmetry is revealed, the physics of the high T_c superconductivity is as simple as the "spin flop" transition. We see that equation (18) describes a precession of the superspin about a "fictitious magnetic field", namely the chemical potential. The easy axis of the antiferromagnet translates into the "easy sphere" (n_2, n_3, n_4) while the "easy plane" of the antiferromagnet translates into the "easy superconducting plane" (n_1, n_5). The transition from a antiferromagnetic ground state to a superconducting one is that of a "*superspin flop transition*". In fact the phase diagram of a easy axis antiferromagnet in the temperature and magnetic field plane is very similar to that of a high T_c superconductor in the temperature and chemical potential plane. The complete analogy between these two systems are summarized in the following table.

	$t-J$ model	negative U Hubbard model	antiferromagnet in a B field
symmetry	$SO(5)$	$SO(4)$	$SO(3)$
symmetry generators	$S_\alpha, Q, \pi_\alpha, \pi_\alpha^\dagger$	$S_\alpha, Q, \eta, \eta^\dagger$	S_α
order parameter	superspin	pseudospin	Neel vector
symmetry breaking	μ	μ	B
phase transition	superspin flop (from SDW to d wave superconductivity)	pseudospin flop (from CDW to s wave superconductivity)	spin flop (from easy axis to easy plane)
collective modes	1 massless phase and 3 massive SDW modes	1 massless phase and 1 massive CDW mode	1 massless XY and 1 massive Z mode

This analogy also helps us to understand the origin of the superspin flop transition in the Hamiltonian formulation of the problem. In the Hamiltonian formulation, the chemical

potential term appear as a coupling to the symmetry generator L_{15}, the number operator Q, but not to the superspin n_a directly. It is not immediately obvious why this term would select any particular direction in the superspin space. Of course, the same problem occurs in the antiferromagnetic analogy, where the uniform magnetic field couples to the total spin vector, not the Neel vector. If one tries to visualize the the Neel Hamiltonian in a semi-classical fashion, one has to remember that there is a important constraint that the total spin vector is orthogonal to the Neel vector. The externally applied uniform magnetic field leads to a finite total spin in the z direction. In order to satisfy the orthogonality condition, the Neel vector therefore has to lie in the plane orthogonal to z. In the present model, (restricting to the $SO(5)$ symmetric case to simplify the algebra), the orthogonality constraint takes the form

$$\epsilon^{abcde} n_c L_{de} = 0 \tag{23}$$

which can be simply proved by expressing the angular momenta in terms of the angular velocities $L_{ab} = \chi(n_a \dot{n}_b - n_b \dot{n}_a)$. The chemical potential term leads to doping, or prefer a finite value L_{15}. We immediately see that the constraint equation gives $n_2 = n_3 = n_4 = 0$ if other L_{ab} generator have no ground state expectation value, which is the case since $\chi > 0$.

The question of the origin of superconductivity is not one question, but rather two related questions separated by a energy scale. The "high energy" mechanism leads to binding of electrons into singlet pairs. The origin of this binding is rather obvious in the $t - J$ model, since the J term favors electrons on near neighbor sites to be antiparallel. The problem is that this same J could also lead to antiferromangetism. In our new language, this pair binding gives rise to a finite magnitude of the superspin, leaving its orientation still unfixed. This is in marked contrast to the celebrated Bardeen-Cooper-Schrieffer theory of conventional superconductivity where pair binding is equated with the onset of superconductivity, and also different from the large phase fluctuation picture [11] where the only uncertainty of the order parameter is its phase. In addition to the high energy pair binding mechanism, a "low energy" mechanism selects a orientation of the superspin and distinguishes antiferro-

magnetism from superconductivity. The selection of the different possible ground states are described by $SO(5)$ nonlinear σ model and the mechanism for favoring superconductivity is the "superspin flop" mechanism discussed above. We see explicitly that *superconductivity is a inevitable consequence of the $SO(5)$ symmetry and antiferromagnetism at half filling.* From this point of view, a antiferromagnet state can in some sense be thought of as a solid formed by Cooper pairs, and the "superspin flop" transition is a first order melting transition from the solid into a superfluid of the Cooper pairs. In this frame work, the "spin fluctuation exchange" calculation [12,8] should be interpreted as a mean field theory of T_{MF}. Such calculations are important parts of our understanding, and lead to the glorious prediction of d superconductivity, but they are not complete since they do not address the actual phase transition and the competition between antiferromagnetism and superconductivity. The two different mechanisms compliment each other in their respective energy regime and together form a complete picture of the origin of superconductivity in the oxides.

Theory of collective modes and their nonlinear interactions The superspin model gives a natural description of the collective modes in the ordered phase. Close to the transition between the antiferromagnetic and the superconducting ground states, the ordered phases are not conventional, but their low energy excitations reflect the competition between the two different kinds of ordering. These low energy excitations can be studied systematically by applying symmetry principles and they have profound experimental consequences which we shall discuss in this section.

Before performing concrete calculations lets us first address the qualitative features of the low energy excitations using symmetry principles. Let us first suppose that the $SO(5)$ symmetry were exact. In this case, if the superspin has a fixed orientation in its ground state, this state breaks the $SO(5)$ symmetry spontaneously. Spontaneous breaking of a continuous symmetry naturally leads to Goldstone bosons. The number of the Goldstone bosons is the number of the *broken* symmetry generators. A fixed direction of the superspin leaves the $SO(4)$ subgroup of the $SO(5)$ unbroken. The $SO(5)$ group has 10 generators, while the $SO(4)$ group has 6 generators. Therefore, we would expect to have 4 Goldstone

bosons, corresponding to the 4 broken symmetry generators.

What is the nature of these 4 Goldstone bosons? Suppose that the superspin vector lies in the superconducting plane, say along the n_1 direction. The mode corresponding to the broken rotation generator L_{15} is just the usual Goldstone mode, describing the phase degrees of freedom of the superconducting order parameter. The three other modes corresponds to the broken generators L_{12}, L_{13} and L_{14}. These modes form a triplet representation of the unbroken $SO(3)$ spin symmetry. On the other hand, if the superspin vector lies in the antiferromagnetic sphere, say along the n_2 direction, the usual spin waves corresponds to the broken generators L_{23} and L_{24}. They do not form a representation of the spin $SO(3)$ group, since this symmetry is spontaneously broken. In addition to the usual spin waves, the current theory predicts two additional Goldstone modes, corresponding to the broken generators L_{21} and L_{25}. They form a doublet representation of the charge $U(1)$ symmetry group.

This symmetry analysis make it clear what happens if the $SO(5)$ symmetry is explicitly broken to $SO(3) \times U(1)$. In the presence of a quadratic symmetry breaking term $g_{eff} = g - \chi(2\mu)^2$, the spin triplet Goldstone mode of the superconducting state would become massive if $g_{eff} < 0$ and the charge doublet mode of the antiferromagnetic state would become massive if $g_{eff} > 0$. The usual spin wave modes and the phase mode remain massless because of the $SO(3) \times U(1)$ symmetry. Goldstone bosons which become massive because of explicit symmetry breaking terms are sometimes called pseudo Goldstone bosons.

This general symmetry analysis can be easily checked by a explicit calculation starting from the $\mathcal{H}_a$. The equations of motion derived from this Hamiltonian takes the form

$$\begin{aligned}\dot{L}_{ab}(x) = & \frac{1}{2}\sum_c (\chi_{ac}^{-1} - \chi_{bc}^{-1})\{L_{ac}(x), L_{bc}(x)\} + \sum_c (\rho_{ac} - \rho_{bc}) v_{ac}^k(x) v_{bc}^k(x) \\ & + \partial_k \sum_c (\rho_{ac} n_b n_c v_{ac}^k(x) - \rho_{bc} n_a n_c v_{bc}^k(x)) + \sum_c (B_{ac} L_{bc}(x) - B_{bc} L_{ac}(x)) \\ & + g \sum_{\alpha=2,3,4} (n_a \delta_{b\alpha} n_\alpha - n_b \delta_{a\alpha} n_\alpha) \end{aligned} \tag{24}$$

$$L_{ab}(x) = \chi_{ab}\omega_{ab} \tag{25}$$

where ω_{ab} is given by the Wick rotation of equation (18). The first term on the right hand

side describe the *local* motion of a five dimensional asymmetrical top, a simple generalization from the equations of motion of a asymmetrical top in classical rigid body mechanics. The second term arises from the asymmetrical coupling of the neighboring rotors. The third term is the most relevant one for our discussion. It arises mathematically from the Schwinger term, proportional to the derivative of a delta function, in the local commutator between $L_{ab}(x)$ and $v^k_{cd}(y)$, and expresses the anomaly content of the $SO(5)$ current algebra. In the absence of the other terms on the right hand side, there are ten conserved charges, and this term describes the conserved currents associated with these charges. The fourth term simply describes the precessional motion of $L_{ab}(x)$ in the presence of a external field, and the last term describe the local torque due to the anisotropy potential. It is easy to see that for $Q(x)$ and $S_\alpha(x)$, only the third term is nonvanishing, expressing the continuity of these exactly conserved charges.

This set of equations are the nonabelian generalization of the familiar Josephson equations [23] in conventional superconductors. The first equation is the generalization of the Josephson current relation. If we take $L_{ab}(x)$ to be $L_{15}(x)$ in the first equation, we find that the only surviving term is the third one, which reduces to the standard Josephson current expression $\vec{J} = \rho_c \vec{\nabla}\theta$ in the isotropic limit. The second equation is the generalization of the Josephson acceleration equation. If we take $L_{ab}(x)$ to be $L_{15}(x)$ in this equation, we recover the familiar *ac* Josephson equation $\mu = d\theta/dt$. This set of equations are also generalization of the Landau-Lifshitz-Neel equation of antiferromagnets [24]. This statement can be easily checked if we take $L_{ab}(x)$ to be $L_{23}(x)$, $L_{24}(x)$ and $L_{34}(x)$ in the above two equations.

This set of equations are the fundamental equations of the high T_c superconductors. They unify the treatment of antiferromagnetim with superconductivity and describe the linear spectrum and the nonlinear interactions of the collective modes in the antiferromagnetic and the superconducting phases. The new physics contained in these equation can be easily analyzed in the linearized approximation. For $g_{eff} > 0$, the ground state is antiferromagnetic, we can linearize the equations around the Neel vector, say n_2, and we obtain

$$\chi_s \partial_t^2 n_\alpha = \rho_s \partial_k^2 n_\alpha \ , \ \alpha = 3,4 \ \ ; \ \ \chi_\pi \partial_t^2 n_\lambda = \rho_\pi \partial_k^2 n_\lambda - (g - (2\mu)^2 \chi_\pi) n_\lambda \ , \ \lambda = 1,5 \qquad (26)$$

The first equation describe the two spin wave modes of the antiferromagnet, while the second equation predicts a new, massive doublet pairing mode. This mode is the precursor of superconductivity in the antiferromagnetic phase. This mode also makes it plausible that one can think of a antiferromagnet as a quantum solid of Cooper pairs. A quantum solid has two types of excitations, the gapless phonon modes, and a gapful mode corresponding to extracting a atom from its position [23]. The pairing mode described in the above equation roughly corresponds to the second type of excitation of a solid, if we identify the Cooper pair as a "atom" of the solid. We see that as the chemical potential is increased, this pairing mode lowers its energy, the quantum solid becomes softer, and eventually the solid melts completely to form a superfluid of Cooper pairs.

For $g_{eff} < 0$, the ground state is superconducting, and we can linearize the equations around the n_1 vector to obtain

$$\chi_c \partial_t^2 n_5 = \rho_c \partial_k^2 n_5 \ \ ; \ \ \chi_\pi \partial_t^2 n_\alpha = \rho_\pi \partial_k^2 n_\alpha - ((2\mu)^2 \chi_\pi - g) n_\alpha \ \ , \ \ \alpha = 2,3,4 \qquad (27)$$

The first equation describe the usual Goldstone mode (sound mode) of a superconductor, while the second equation describe the triplet of massive magnetic modes predicted by Demler and Zhang [15]. This mode is a precursor of antiferromagnetism in the superconducting phase. It can be roughly thought of as the roton mode in a superfluid, since they both reflect the "diagonal short range order" in a superfluid. As the chemical potential is decreased, this mode lowers its energy and eventually the superfluid "solidifies" to form a antiferromagnet.

Both the doublet pairing mode in the antiferromagnetic phase and the triplet magnetic mode in the superconducting phase owe their existance to the kinetic energy terms of the π operators. Therefore, we shall call them the π doublet and the π triplet modes respectively.

Both classes of new collective modes have important experimental consequences. The π triplet mode has been used by Demler and Zhang [15] to explain the recent resonant neutron scattering experiments on $YBCO$ superconductors. It was found that below the superconducting transition temperature, a collective excitation peak appears in the neutron

scattering cross section. The energies of the mode range from $25meV$ to $41meV$ [25–29] depending on doping level, and the scatterings are observed in the spin triplet channel, at the commensurate momentum (π, π, π), in exact agreement with the quantum numbers found theoretically. These modes vanish exactly at T_c [27,28], consistent with the interpretation that they are the pseudo-Goldstone modes associated with the $U(1)$ symmetry breaking. The precise correlation between the energy of the neutron peak and the superconducting transition temperature will be discussed in a later section.

The π doublet mode of a doped antiferromagnetic state is much harder to observe experimentally. But they have indirect consequences which can be measured. In a puzzling experiment, Suzuki it et al. [30] observed a unusually long Josephson coupling length of up to $480\mathring{A}$ in the $YBa_2Cu_3O_7/PrBa_2Cu_3O_7/YBa_2Cu_3O_7$ junction. This experiment could be interpreted as a signature of the small gap towards the π doublet pairing excitation in the insulating material $PrBa_2Cu_3O_7$.

All above discussion assume that quantum fluctuations are not strong enough to destroy the long range order. In the opposite limit, when $\chi^{-1} >> \rho$, one should diagonalize the kinetic terms in $\mathcal{H}_s$ and $\mathcal{H}_a$ first and treat the potenial energy terms as perturbation. The kinetic terms can be diagonalized easily by using the representation theory of $SO(n)$. They classified by a integer l, and the Casimir operator has the value of $l(l+n-2)$ in this representation. The ground state is a $SO(5)$ singlet with $l = 0$, and the lowest energy excitation is a massive vector multiplet with $l = 1$. This multiplet is split by the anisotropy in the kinetic coefficients. The massive pairing doublet has a energy of $\frac{1}{2\chi_c} + \frac{3}{2\chi_\pi}$ while the massive magnetic triplet has a energy of $\frac{2}{2\chi_s} + \frac{2}{2\chi_\pi}$.

The global phase diagram of high T_c superconductors It is straightforward to determine the phase diagram of the $SO(5)$ nonlinear σ model and compare it with the experimentally observed phase diagram of high T_c superconductors. The topology of the phase diagram takes different form depending on the strength of the quantum fluctuation. In the following, we will always be discussing the case of $d = 3$, unless otherwise stated. Our model does not have any disorder, therefore any disorder induced phase such as spin glass

is precluded in the current discussion.

Let us first discuss the so called renormalized classical regime [6], where quantum fluctuations merely renormalize the coupling constants of the model, but they are not strong enough to destroy the various types of ordering. In this case, at half filling, $\mu = 0$ and $g > 0$, the superspin lies in the "easy sphere" (n_2, n_3, n_4) and the ground state is antiferromagnetic. There is a phase transition at T_N to a paramagnetic phase as the temperature is raised, and this phase transition is in the universality class of the classical $SO(3)$ model in three dimensions. When the chemical potential is increased from its half filling value of $\mu = 0$, the gap towards the π doublet mode decreases. Since it is easier for the superspin to fluctuate into other directions, the effective spin stiffness decreases and so does the Neel temperature. At the critical value $\mu = \mu_c$, the superspin has no preferential "easy directions", and the system is described by a isotropic $SO(5)$ nonlinear σ model. This model has its own critical temperature T_{bc}, which is in general smaller than the Neel temperature, since the critical temperature of the $SO(N)$ model scales inversely with N. If the $\mu = \mu_c$ line is reached when $T < T_{bc}$, the system is ordered and the superspin defined in this limiting procedure still lies within antiferromagnetic "easy sphere". When μ is increased beyond the critical value, the superspin "flops" into the superconducting plane. Since the direction of the superspin changes abruptly at the transition, and since at the transition point, the correlation length in the sense of Josephson is finite, the "superspin flop" transition in general first order for $T < T_{bc}$. Beyond the superspin flop transition, the system crosses from a $SO(5)$ critical behavior over to a XY critical behavior, and one expects the superconducting transition temperature to increase with increasing chemical potential, since the mass of the π triplet mode increases. The topology of the phase diagram in this case is depicted in Fig. (1a).

The line of the first order superspin flop transition is in general not exactly vertical, since the susceptibilities and the stiffness in different superspin directions may not be the same. At zero temperature and for $\mu < \mu_c$, $Q = 0$, the density of holes vanish. For $\mu > \mu_c$, the density of holes is finite. The discontinuous jump of the density is given by $2\chi\mu_c$. The reason for the hole density to vanish when $\mu < \mu_c$ is because we employed a superspin model with

a fixed magnitude. When one relaxes the model to a "soft superspin" one, the hole density can be finite in this region. However, the discontinuous jump in the density will remain in the "soft superspin" model. Because there is a discontinuous jump in the density, for hole concentrations in the "forbidden region" $0 < Q < 2\chi\mu_c$, the system phase separates into a hole rich and a hole deficient region, a possibility first pointed out by Emery, Kivelson and Lin [4] in the context of the $t-J$ model. The physics in the "forbidden density region" could be rather complicated, and interactions not included in our current model could give rise to various types of ordering, such as incommensurate order and "stripe phases". However, we believe that this types of order are not directly related to the origin of superconductivity.

The first order superspin flop line terminates at a critical point, from which two second order lines, one corresponding to the Neel transition and the other corresponding to the XY transition, emerge. For this reason, this critical point is called a bi-critical point. There are two relevant operators in the close vicinity of the bi-critical point, the reduced temperature $t = (T - T_{bc})/T_{bc}$ and g_{eff}. The scaling behavior close to this point is well studied in the literature [31–34]. One of the most important result is that even if the model defined at the short length scales is not exactly $SO(N)$ invariant, *i.e.* the susceptibility and stiffness in different directions may not be the same, the difference among them scales to zero under the renormalization group flow when the bi-critical point is reached. A simple version of this result is shown by Pelcovit and Nelson [32], who considers a $SO(N)$ model where the the $N-th$ component has a different stiffness than the others. They have shown that the difference operator has negative scaling dimension in the $2+\epsilon$ expansion of the nonlinear σ model, and is therefore irrelevant close to the critical point. A more general and very elegant result was derived by Friedan [35], who considers a nonlinear σ model in a arbitrary Riemanian manifold with metric g_{ab}. Friedan showed that the fixed point of the renormalization group flow is a Einstein manifold with $g_{ab} = \frac{1}{2\pi(d-2)} R_{ab}$, where R_{ab} is the Ricci tensor. In particular, if one starts with a distorted sphere S_n, only the average curvature is a relevant variable, whereas the distortions preserving the average curvature are irrelevant. Therefore, if one has a microscopic model without the full spherical symmetry,

a perfect sphere with constant curvature is produced by the large scale fluctuations close to the critical point. This result provides a strong theoretical justification to describe the high T_c superconductors by a $SO(5)$ nonlinear σ model: *Even if the symmetry is only approximately valid in the microscopic models such as the Hubbard or the $t-J$ model, close to the bi-critical point, where the most interesting transition from a antiferromagnetic state to a superconducting state occurs, this symmetry becomes exact.*

Close to the bicritical point, thermodynamic quantities obey exact scaling relations. As mentioned before, there are two relevant operators in the problem. Finite t gives a temperature correlation length according to the scaling law $\xi_t \sim t^{-\nu}$. The other relevant parameter is the biquadratic symmetry breaking term g_{eff}, which gives a correlation length $\xi_g \sim g_{eff}^{-\nu_g}$ Close to the bicritical point, the singular part of the free energy scales according

$$f(t, g_{eff}) \sim t^{2-\alpha} \tilde{f}(A g_{eff}/t^{\phi}) \tag{28}$$

where α is the free energy exponent of the $SO(5)$ model and ϕ is a crossover exponent given by $\phi = \nu/\nu_g$. In equation (28), A is a non-universal constant and $\tilde{f}$ is a universal scaling function of a single argument. Other singular thermodynamic quantities are be determined in a similar way.

The crossover exponent ϕ determines the way in which the two second order lines merge into the first order line. The universal scaling function $\tilde{f}$ diverges at two arguments, $x_+ > 0$ and $x_- < 0$. The two second order lines are determined by

$$g_{eff} = (x_+/A)t^{\phi} \quad , \quad g_{eff} = (x_-/A)t^{\phi} \tag{29}$$

Explicit calculations of the exponents can be carried out within the large N approximation [36]. To the leading order, $\nu = 1$ and $\nu_g = 1/2$, therefore $\phi = 2$. From this we conclude that the two second order lines merge into the first order line tangentially. (See Figure (1a)).

As we have seen before, there exist parameter regimes where antiferromagnetism and superconductivity can both coexist. In this case, the topology of the phase diagram has to be modified to include the immediate mixed phase, the "spin bag" phase [5]. The "spin bag"

phase is conceptually similar to the conjectured supersolid phase in ^4H_e. In this case, part or the entire first order superspin flop lines separates into two second order lines enclosing the "spin bag" phase. (See Figure (1b)). The four second order lines intersect at a tetracritical point T_{tc}.

So far all phase transitions discussed are classical phase transitions, in the sense that quantum mechanical fluctuations only renormalize the coupling constants in the problem. When quantum fluctuation is gradually increased, ordering in some phases can be destroyed. Since the $SO(5)$ isotropic point has the largest quantum fluctuation, one would expect T_{bc} to be driven to zero first. In this case, the bicritical point is a quantum critical point where the antiferromagnetic state goes into the superconducting state via a direct second order phase transition. (See Figure (1c)).

When the quantum fluctuations are increased further, a entire region between the antiferromagnetic phase and the superconducting phase becomes quantum disordered. (See Figure (1d)). In this region, the properties of the model are better described by first diagonalizing the kinetic energy term of the Hamitonian. Both the triplet magnetic excitations and the doublet pairing excitations have finite energy gaps. The transition from the quantum disordered phase into the antiferromagnetic phase is second order, the doublet pairing mode of the quantum disordered phase naturally continues into the π doublet mode in the antiferromagnetic phase, while the triplet magnetic excitation of the quantum disordered phase becomes the two gapless Goldstone modes of the antiferromagnetic phase. The transition from the quantum disordered phase into the superconducting phase is second order as well, the triplet magnetic excitation of the quantum disordered phase naturally continues into the π triplet mode of the superconducting phase,[2] while the doublet pairing mode becomes the gapless Goldstone mode of the superconductor.

---

[2]I would like to thank Prof. T.M. Rice for a stimulating discussion which lead me to this identification.

The $SO(5)$ quantum disordered phase differ from the $SO(3)$ quantum disordered phase of the quantum antiferromagnet [6] and the quantum XY disordered phase [10] since it has both a massive triplet magnetic excitation and a massive doublet of pairing excitation. It is tempting to identify it with the resonating-valence-bond (RVB) phase introduced by Anderson. In fact, the type (1d) phase diagram looks very similar to the original RVB idea proposed by Anderson [1]. The basic idea is that with low dimensionality and increased doping, quantum fluctuations will first "melt" the antiferromagnetic state to form a resonating valence bond liquid of spin singlet pairs, and these singlet pairs further condense into a superfluid state. However, the $SO(5)$ quantum disordered phase differ from Anderson's RVB phase in terms of the excitation spectrum. In the RVB phase, spinons and holons are the elementary excitations, while in the $SO(5)$ quantum disordered phase, even the electrons are "bound" into the collective coordinates. In some sense, the $SO(5)$ quantum disordered phase describe a "incompressible liquid" of singlet pairs, similar to the Laughlin liquid in the fractional quantum Hall effect.

We therefore see that the global features of the phase diagram deduced from the $SO(5)$ quantum nonlinear σ model agree reasonablly well with the general topology of the experimentally observed phase diagram of high T_c superconductors. With this model, we can understand the depression of the Neel and the superconducting temperature in terms of a common origin, namely a region in the phase diagram where the $SO(5)$ fluctuations are maximal. This theory makes precise predictions about the scaling behavior in the crossover region. These predictions can be tested experimentally in sufficiently clean systems where a direct first order transition becomes possible. I believe that phase diagrams of the type (1a) or (1c) are reasonablly close to the reality in the high T_c superconductors. Type (1b) may be useful to understand the heavy fermion materials, while type (1d) could be realized in the quasi one dimensional ladder systems where quantum fluctuations are strong.

Theory of the spin gap, the superconducting transition and their relationship One of the most interesting phenomenon of the underdoped high T_c materials is the so called spin gap. Above a certain temperature T_s, the magnetic correlation length increases with

decreasing temperature, while it saturates below $T_s > T_c$. This phenomenon has only been observed in the $YBCO$ family of the high T_c superconductors. The spin gap phenomenon has been observed in two different kinds of nuclear spin relaxation processes, the $1/T_1$ and $1/T_{2G}$ measurements respectively. Through a series of insightful phenomenological analysis of the NMR experiments, Sokol and Pines [37] concluded that this two experiments can be linked through a simple $z = 1$ dynamical scaling hypothesis. Since our model is Lorentz invariant, their hypothesis is valid here. Therefore, we shall only address here the $1/T_{2G}$ experiment, which meausures the static spin correlation length.

The phenomenon of spin gap has a natural explanation within the current theoretical model. There are three different temperature scales in the current model. When the temperature is lowered below T_{MF}, the superspin vector acquires a finite magnitude. However, for a finite range of temperature below T_{MF}, say $T_s < T < T_{MF}$, (see Fig. 1), the temperature scales is still high enough so that the superspin does not "notice" the anisotropy is its orientational degrees of freedom. In this range of temperature, the model is essentially $SO(5)$ symmetric, and the antiferromagnetic correlation length increases together with the pairing correlation length as temperature is lowered. For $T < T_s$, the thermal energy becomes low compared to the anisotropy energy in the superspin space, and the superspin vector lies preferably in the superconducting plane. Therefore, below T_s, the antiferromagnetic correlation length saturates to a finite value. Finally, at T_c, the superspin vector picks a particular direction within the superconducting plane, therefore breaking the $U(1)$ gauge symmetry, and the system becomes superconducting. A very similar picture applies to the antiferromagnetic side of the transition. There is a "pairing gap" temperature T_p, above which the pairing correlation length increases together with the antiferromagnetic correlation length, while it saturates below T_p.

Both T_s and T_c can be calculated quantitatively within the $SO(5)$ nonlinear σ model. In principle, one can perform the calculation for all four types of phase diagrams shown in Fig. 1. Due to the space limitation, we will only show the calculation for a representative case, the case (1c), where the transition from antiferromagnetism to superconductivity occurs via

a zero temperature quantum critical point. Since the anisotropy is irrelevant near the critical point, we will take the model to be isotropic. The idea of the large N mean field theory is to implement the constraint in the partition function (19) through a Lagrangian multiplier λ and determine the value of λ through a self-consistency condition that $n_a^2 = 1$ is enforced on average. Skipping the intermediate steps [9], the resulting self-consistency condition is given by

$$2\chi = 2\int_0^{a^{-1}} \frac{d^3q}{(2\pi)^3} \frac{1}{\sqrt{c^2q^2 + c^2\xi^{-2}}\ tanh(\frac{\beta}{2}\sqrt{c^2q^2 + c^2\xi^{-2}})} + 3\int_0^{a^{-1}} \frac{d^3q}{(2\pi)^3} \frac{1}{\sqrt{c^2q^2 + c^2\xi^{-2} + \omega_0^2}\ tanh(\frac{\beta}{2}\sqrt{c^2q^2 + c^2\xi^{-2} + \omega_0^2})} \tag{30}$$

Here a is a lattice cutoff, ξ is the superconducting correlation length, $\omega_0^2 = (2\mu)^2 - (2\mu_c)^2$ is the energy of the π triplet mode in the superconducting state, $\xi_s^{-2} = \xi^{-2} + (\omega_0/c)^2$ is the antiferromagnetic correlation length and $c = \sqrt{\rho/\chi}$ is the sound or spin wave velocity.

The quantum bicritical point is determined by the condition that at $\omega_0 = 0$, ξ diverges at zero temperature. This determines

$$\sqrt{\rho\chi} = \frac{5}{8\pi^2}a^{-2} \tag{31}$$

to be the condition for the quantum bi-critical point. When ω_0 is greater than zero, ξ diverges at a finite temperature T_c. The relationship between these two quantities can be easily determined from equation (30), and is found to be

$$\frac{\omega_0^2}{(kT_c)^2}(\frac{3}{2}x^2 - 3f(x)) \approx 16.44 \tag{32}$$

where $x = ca^{-1}/\omega_0 = \xi_s/a$ is the antiferromagnetic length at zero temperature, and $f(x) = \frac{1}{2}x\sqrt{x^2+1} - \frac{1}{2}ln(x + \sqrt{x^2+1})$. We see here that up to a logarithmic term, ω_0 and kT_c are simply proportional to each other. This fact can be understood without any explicit calculations. At $\omega_0 = 0$, the correlation length at a finite temperature is simply given by the Lorentz transformation of the finite width β in the imaginary time direction, or the thermal de Broglie wave length $\hbar c/kT$. At $T = 0$ and finite ω_0, the correlation length can be

estimated from power counting the scaling dimension of ω_0, which gives c/ω_0. Equating these two length scales and neglecting the logarithmic corrections gives the estimate of $kT_c \propto \omega_0$.

Let us now turn to the calculation of the spin gap temperature T_s. From the form of the antiferromagnetic correlation length $\xi_s^{-2} = \xi^{-2} + (\omega_0/c)^2$, (a very similar form was first used by Millis, Monien and Pines [38] in their phenomenological analysis of the NMR data), we see that at high temperature, the second term is smaller than the first, therefore, ξ_s depends on temperature in the same way ξ does, namely proportional to the thermal de Broglie wave length $\hbar c/kT$. However, at low temperature, the second term dominates, and ξ_s saturates to a finite, temperature independent value. The spin gap temperature can therefore be defined by $c^2\xi^{-2}(T_s) = \omega_0^2$. Inserting this definition into equation (30), we obtain a explicit formula for the spin gap temperature

$$\frac{\omega_0^2}{(kT_s)^2}(\frac{5}{2}x^2 - 2f(x) - 6f(x/\sqrt{2})) \approx 16.44 \tag{33}$$

Equations (32) and (33) relates three experimentally observable quantities, the superconducting transition temperature T_c, the spin gap temperature T_s and the resonant neutron scattering peak ω_0 to each other. ξ_s is the zero temperature antiferromagnetic correlation length averaged over three space dimensions. Since there are some uncertainies about the correlation length in the c axis and the value of the microscopic cutoff of the σ model, we shall take ξ_s/a as a fitting parameter.

The relation between the energy of the resonant neutron scattering peak and T_c has been measured recently in the $YBa_2Cu_3O_{6+x}$ superconductors by Fong *et al* [28]. It was found that ω_0 is linearly proportional to T_c with a slope of about 5.6. If we take ξ_s/a to be 0.8 in equation (32) and roughly doping independent in the doping regimes explored in experiment, our theory gives the same slope. Notice that since ξ_s/a is a three dimensional average, the actual antiferromagnetic correlation length in the two dimensional sheet could be much greater.

Combining the result of this section and the previous section on the collective modes, we see that the current work offers a unique explanation of the recent neutron scattering

experiment of the high T_c superconductors in terms of the pseudo-Goldstone bosons associates with the spontaneous $SO(5)$ symmetry breaking. Since these magnetic excitations occur only below the superconducting transition temperature, the interpretation in terms of the Goldstone bosons is most natural, and we see that the linear proportionality between T_c and ω_0 is also naturally explained within the current theoretical model. A class of theoretical models [27,39–41,7,42] attempt to associate the neutron resonance peak with the opening up of a d wave pairing gap, and possible excitonic states inside this gap. At the time when this class of theories were proposed, only a $41meV$ peak was observed in the optimally doped $YBCO$ superconductor [25–27]. However, recent photoemission [43] and resonant neutron scattering [28,29] experiments in the underdoped regime can not be reconciled with this class of theories. In the underdoped regime, the electronic energy gap opens up at a temperature much higher than T_c. If the resonant neutron scattering peak arises simply from the removal of spectral weight due to the electronic gap opening, such a peak would be observed far above T_c, in contradiction to the experimental observation [28,29]. In this class of theories, the energy of the neutron scattering peak would also be proportional to the electronic gap energy. As the doping level is decreased from the optimal value, the electronic energy gap actually increases slightly [44]. Therefore, this class of theories would predict that the energy of the neutron resonance increases with decreasing doping, also in contradiction with the recent experiment by Fong *et al.* [28].

This value of $\xi_s/a \approx 0.8$ can now be used to estimate the spin gap temperature without any additional fitting parameter. From equation (32) and (33), we find $T_s/T_c \approx 1.37$. There are some experimental uncertainties about the value of T_s as well. The most acurate measurement of T_s is in the $T_c = 62K$ material $YBa_2Cu_3O_{6.63}$. The $1/T_{2G}$ measurement shows that the antiferromagnetic correlation length saturate at $T_s \approx 100K$ [45]. This gives a T_s/T_c ratio of 1.61, about 15% higher than the theoretically predicted ratio.

We would like to remark that these quantitative calculations are strictly speaking only valid near the critical doping, while most of the experiments quoted above are far from it. It would be highly desirable to have sufficiently clean systems close to the critical doping

where precise comparison with theory can be made.

Attempt at a synthesis The most important message from this work is that antiferromagnetism and superconductivity are the two different sides of the same coin. They are intimately related by a $SO(5)$ symmetry which determines the competition and the low energy dynamics of the high T_c superconductors. The current theory offers a unified explanation of some of the most challenging problems of high T_c superconductivity.

This work answers a number of experimental puzzles. The mechanism of superconductivity is devided into a "high energy" piece, identified with the pair binding, or the formation of the amplitude of the superspin and a "low energy" piece, involving a "superspin flop" mechanism which selects the orientation of the superspin, and resolves the competition between superconductivity and antiferromagnetism. These two different energy scales have different doping dependence. With increasing doping, T_{MF} decreases because the effective J decreases, but T_c increases because both the thermal and the quantum $SO(5)$ fluctuations decreases. Recent photoemission experiment [44] indeed found that the electronic gap decreases with increasing T_c, a fact inconsistent with the weak coupling BCS theory, but consistent with the current model. This work also answers the question of why T_c is low compared with the energy scales of the pair formation. Emery and Kivelson [11] rightfully argues that this happens because the superfluid density is low, but did not offer a explanation of why this is so. The current work explains this fact in terms of increased quantum and classical $SO(5)$ fluctuations near the isotropic point μ_c, so that both the Neel temperature and the superconducting transition temperature are depressed in this transition region. The puzzeling spin gap phenomenon is naturally interpreted in terms of the competition between entropy and anisotropy energy in the superspin space. So far the most direct experimental evidence for the approximate $SO(5)$ symmetry is the resonant neutron scattering peaks in the underdoped and optimally doped region. These modes are naturally interpreted in terms of the pseudo Goldstone bosons associated with the spontanuous $SO(5)$ symmetry breaking. Current model predicts that their intensity vanish exactly at T_c, the mode energy is temperature independent, and decreases with decreasing doping. All these facts are consistent

with the experimental findings. Notablly absent in our discussion is the transport properties of the high T_c oxides. Below T_{MF}, transport properties could be addressed by considering fermions coupled to the $SO(5)$ nonlinear σ model degrees of freedom. However, quantitative details have not yet been fully worked out.

The current theory also unifies a number of seeeming divergent theoretical approaches to the high T_c problem. It outlines a strategy to systematically extract the low energy content of the $t-J$ model by constructing low energy field theory constrained by the microscopic symmetry. The $SO(5)$ symmetry can be used as a basic principle to organize the various theoretical proposals. Most directly, it unifies the $SO(3)$ nonlinear σ model theory [6,8,9] with the $U(1)$ nonlinear σ model theory [10,11]. The "spin fluctuation exchange" [12,8] approach should be interpeted as a theory of T_{MF}. the phase separation in the $t-J$ model [4] occurs because the "superspin flop" transition is first order, therefore giving rise to a "forbidden density region". The "spin bag phase" [5] can emerge in the phase diagram as a result of increased π fluctuation, or more precisely when $\chi_\pi > \chi_c$. The $SO(5)$ quantum disordered phase could in some sense be associated with the RVB phase in Anderson's [1] original proposal, and occurs as a result of increased $SO(5)$ quantum fluctuation.

The $SO(5)$ theory makes a number of new experimental predictions. The most direct prediction is that when the materials are sufficiently clean, there could be a direct first order transition between the antiferromagnetic and the superconducting states. Measurements close to the bicritical point can be compared quantitatively with the theoretical predictions and can serve as important test of the theory. There are other predictions, due to the space limitations I shall only outline the basic ideas, and publish the details elsewhere. In the conventional Landau-Ginzburg theory of superconductivity, the order parameter is constrained to lie in a plane. Near the core of a superconducting vortex, a mathematical singularity is unavoidable. However, in the superspin model, since the order parameter is five dimensional, the superspin could lie in the superconducting plane far away from a vortex, but flip into the antiferromagnetic sphere inside a vortex. Such a topological configuration is called a "meron" in the field theory literature, meaning half of a Skyrmion. Therefore,

the current theory would predict that the core of a vortex in underdoped superconductors are not filled with normal electrons but are antiferromagnetic instead. Such a effect could be observed in the dissipation dynamics, or more directly, by studying the form factors of the vortex lattice in neutron scattering experiments. The current theory also predicts that at the interface between a antiferromagnet and a superconductor, the massive π modes become gapless, in very much the same way the collective modes in a Laughlin liquid in the quantum Hall effect become gapless at the edge. Such effects could be observed in tunneling experiments.

High T_c superconductivity is one of the most complex and perplexing phenomena ever encountered in condensed matter physics. Obviously, if there is any hope in completely solving this problem, the solution has to be derived from a simple and unifying principle. The present work is a attempt towards a synthesis of the complex high T_c phenomenology from a symmetry principle which unifies antiferromagnetism with superconductivity. Throughout the history of physics, symmetry principle has been a faithful companion in our quest of the deep unity and harmony of Nature. May this time honored, deeply aesthetic principle help us one more time, to unlock the secret of high T_c superconductivity.

Acknowledgement I would like to thank Prof. J. R. Schrieffer, S. Kivelson, R.B. Laughlin and D. Scalapino for patiently teaching me about various aspects of the high T_c problem throughout the years, and for sharing with me their deep insights and enthusiasm. I would like to thank Prof. C.P. Burgess and C. Lütken for tutoring me about the nonlinear σ model theory of QCD. Inspiring discussions with N. Bulut, E. Demler, H. Fukuyama, W. Hanke, B. Keimer, H. Kohno, S. Meixner, N. Nagaosa and Z.X. Shen are also gratefully acknowledged. Last but not least, I would like to thank Prof. C.N. Yang for collaborating on a earlier work which inspired the current one, and for impressing me with the power of symmetry.

This work is supported by the NSF under grant numbers DMR-9400372 and DMR-9522915. Part of this work is carried out while visiting the IBM Almaden Research Center and I would like to thank Dr. B.A. Jones for the hospitality extended to me during my visit.

REFERENCES

[1] P.W. Anderson. *Science*, 235:1196, 1987.

[2] F.C. Zhang and T.M. Rice. *Phys. Rev. B*, 37:3759, 1988.

[3] P.A. Lee and N. Read. *Phys. Rev. Lett.*, 58:2891, 1987.

[4] V.J. Emery, S. Kivelson, and H.Q. Lin. *Phys. Rev. Lett.*, 64:475, 1990.

[5] J.R. Schrieffer, X.G. Wen, and S.C. Zhang. *Phys. Rev. B*, 39:11663, 1989.

[6] S. Chakravarty, B.I. Halperin, and D.R. Nelson. *Phys. Rev. B*, 39:2344, 1989.

[7] V. Barzykin and D. Pines. *Phys. Rev. B*, 52:13585, 1995.

[8] D. Pines. *Physica C*, 235:113, 1994.

[9] A.V. Chubukov, S. Sachdev, and J. Ye. *Phys. Rev. B*, 49:11919, 1994.

[10] S. Doniach and M. Inui. *Phys. Rev. B*, 41:6668, 1990.

[11] V.J. Emery and S. Kivelson. *Nature*, 374:434, 1995.

[12] D. Scalapino. *Phys. Rep.*, 250:329, 1995.

[13] P.W. Anderson. *Phys. Rev.*, 112:1900, 1958.

[14] S. C. Zhang. *Phys. Rev. Lett.*, 65:120, 1990.

[15] E. Demler and S.C. Zhang. *Phys. Rev. Lett.*, 75:4126, 1995.

[16] H. Kohno, B. Normad, and H. Fukuyama. *Proceedings of 10th Anniversary HTS Workshop*. World Scientific Publishing Company.

[17] E. Demler and S.C. Zhang. to be published.

[18] S. Meixner and W. Hanke. to be published.

[19] C.N. Yang and S.C. Zhang. *Mod. Phys. Lett. B*, 4:759, 1990.

[20] S. C. Zhang. *Int. J. Mod. Phys. B*, 5:153, 1991.

[21] E. Demler, S.C. Zhang, N. Bulut, and D. Scalapino. *Int. J. Mod. Phys. B*, 10:2137, 1996.

[22] C.N. Yang. *Phys. Rev. Lett.*, 63:2144, 1989.

[23] P.W. Anderson. *Basic Notions of Condensed Matter Physics*. The Benjamin/Cummings Publishing Company.

[24] B.I. Halperin and P.C. Hohenberg. *Phys. Rev.*, 188:898, 1969.

[25] J. Rossat-Mignod et al. *Physica C*, 185:86, 1991.

[26] H. Mook et al. *Phys. Rev. Lett.*, 70:3490, 1994.

[27] H.F. Fong et al. *Phys. Rev. Lett.*, 75:316, 1995.

[28] H.F. Fong et al. Superconductivity induced anomalies in the spin exitation spectra of underdoped $YBa_2Cu_3O_{6+x}$. preprint.

[29] P. Dai et al. Magnetic dynamics in underdoped $YBa_2Cu_3O_{7-x}$. preprint.

[30] Y. Suzuki et al. *Phys. Rev. Lett.*, 328:328, 1994.

[31] M.E. Fisher and D.R. Nelson. *Phys. Rev. Lett.*, 32:1350, 1974.

[32] R.A. Pelcovits and D.R. Nelson. *Phys. Lett. A*, 57:23, 1976.

[33] D.R. Nelson and R.A. Pelcovits. *Phys. Rev. B*, 16:2191, 1977.

[34] D.S. Fisher. *Phys. Rev. B*, 39:11783, 1989.

[35] D.H. Friedan. *Annals of Physics*, 163:318, 1985.

[36] S. Hikami and R. Abe. *Prog. Theor. Phys.*, 52:369, 1974.

[37] A. Sokol and D. Pines. *Phys. Rev. Lett.*, 71:2813, 1993.

[38] A.J. Millis, H. Monien, and D. Pines. *Phys. Rev. B*, 42:167, 1990.

[39] N. Bulut and D. Scalapino. *Phys. Rev. B*, 53:5149, 1996.

[40] I.I. Mazin and V.M. Yakovenko. *Phys. Rev. Lett.*, 75:4134, 1995.

[41] D.Z. Liu et al. *Phys. Rev. Lett.*, 75:4130, 1995.

[42] A. Millis and H. Monien. On the bilayer coupling in the yttrium-barium family of high temperature superconductors. preprint.

[43] A.G. Loeser et al. *Science*, 273:325, 1996.

[44] J.M. Harris et al. Anomalous superconducting state gap size vs. t_c behavior in underdoped $Bi_2Sr_2Ca_{1-x}Dy_xCu_2O_{8+\delta}$. preprint.

[45] M. Takigawa. *Phys. Rev. B*, 49:4158, 1994.

FIGURES

FIG. 1. Global phase diagram of high T_c superconductors in the absence of disorder. T_{MF} is the temperature below which electrons bind to form singlet pairs, in the current model, it corresponds a finite magnitude of the superspin. T_N and T_c are the Neel and superconducting transition temperatures respectively. There are four possible types of transitions from the antiferromagnetic to the superconducting state. a) There is a direct first order transition which terminates at a bi-critical point T_{bc}. The first order transition can be described as a "superspin flop" transition. b) There are two second order phase transitions with a intermediate "spin bag" phase. The four second order lines merge at a tetracritical point T_{tc}. c) There is a single second order phase transition at a quantum critical point. d) There are two second order quantum phase transitions with a intermediate quantum disordered phase. In each type of the phase diagrams, there are two crossover temperatures T_s and T_p. The "spin gap" temperature T_s corresponds to the temperature below which the superspin lies within the the superconducting plane, and "pairing gap" temperature T_p corresponds to the temperature below which the superspin lies within antiferromagnetic sphere.

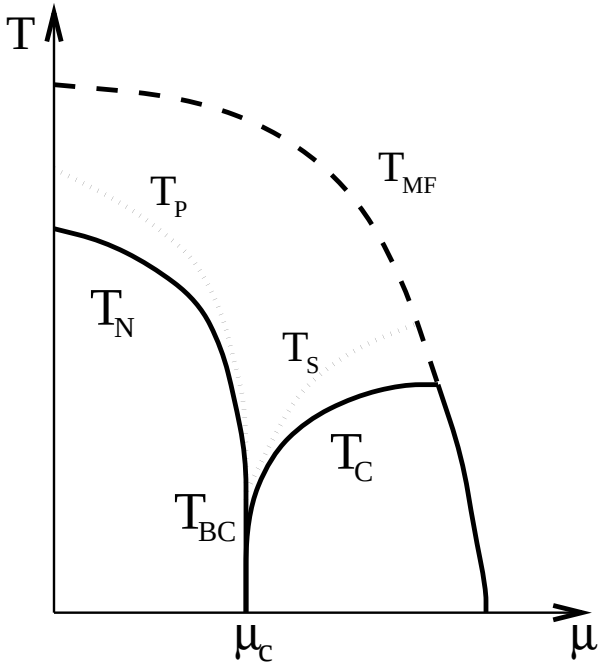
T
T_MF
T_P
T_N
T_S
T_C
T_BC
μ_c
μ

(a)

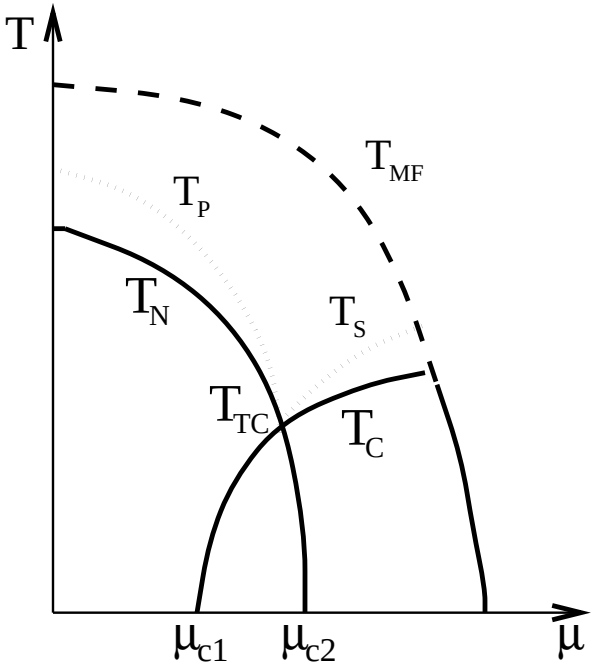
T
T_MF
T_P
T_N
T_S
T_TC
T_C
μ_c1
μ_c2
μ

(b)

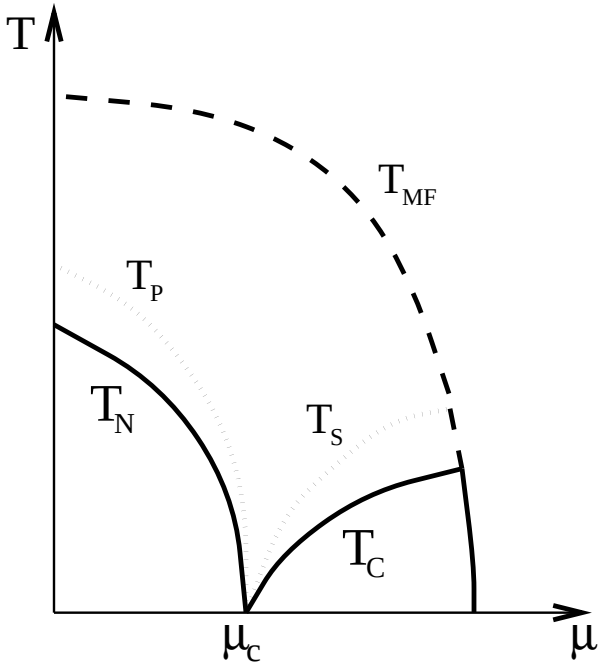
T
T_MF
T_P
T_N
T_S
T_C
μ_c
μ

(c)

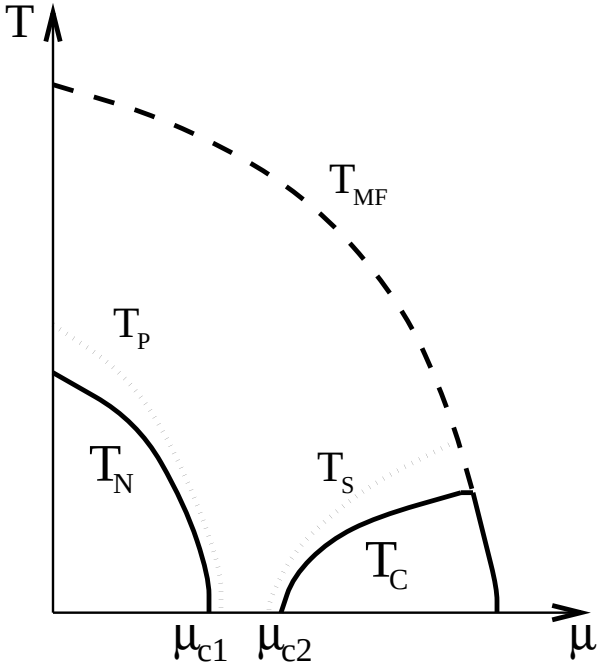
T
T_MF
T_P
T_N
T_S
T_C
μ_c1
μ_c2
μ

(d)